

**FABRICATION AND CHARACTERIZATION OF  
HYBRID MICROWAVE ASSISTED SINTERING  
Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> COMPOSITE SOLDER**

**FLORA SOMIDIN**

**UNIVERSITI MALAYSIA PERLIS  
2015**

© This item is protected by original copyright



**Fabrication and Characterization of  
Hybrid Microwave Assisted Sintering  
Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> Composite Solder**

By

**Flora Somidin  
(1230410796)**

A Thesis Submitted in Fulfillment of the requirements for the degree of  
Master of Science (Materials Engineering)

**School of Materials Engineering  
UNIVERSITI MALAYSIA PERLIS  
2015**

## APPROVAL AND DECLARATION SHEET

This thesis titled Fabrication and Characterization of Hybrid Microwave Assisted Sintering Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> Composite Solder was prepared and submitted by Flora Somidin (Matrix Number: 1230410796) and has been found satisfactory in terms of scope, quality and presentation as partial fulfillment of the requirement for the award of degree of Master of Science (Materials Engineering) in University Malaysia Perlis (UniMAP).

Check and Approved by



.....  
**(MOHD ARIF ANUAR MOHD SALLEH)**

Project Supervisor

School of Materials Engineering

Universiti Malaysia Perlis

(Date: ..... 1/11/2014 .....)

School of Materials Engineering

Universiti Malaysia Perlis

2014

## AKNOWLEDGEMENT

I would like to take this opportunity to express my heartiest gratitude to those who have provided me with help along the way, and the people who have shaped the person I am today.

First of all, I would like to express my best and sincere thanks to my main supervisor, Mr. Mohd Arif Anuar Mohd Salleh for his continuous assistance, uncountable help and guidance, throughout the whole process to complete my research. He managed to teach me how to work independently, but at any time, his useful advice was continuously available to me. His enthusiasm for composite solder technology has always invigorated me with a desire to investigate new and interesting topics. I deeply feel that my success is directly linked to his guidance.

I am also grateful to my co-supervisor, Dr. Norainiza Saud for her patient guidance, constant encouragement and invaluable suggestions for my research work. Her confidence in my capabilities has given me immense opportunities to stimulate my research potential. I greatly appreciate her continuous guidance and support. I am also would like to thank my co-supervisor from Universiti Sains Malaysia (USM), Prof. Dr. Zainal Ariffin Ahmad, who generously accommodated this research project by providing materials for the assembly of hybrid microwave assisted sintering setup and sharing his huge work experience on this research topic. His supports were extremely necessary for finishing this dissertation.

A lot of thanks to Dr. Mohd Mustafa Al Bakri Abdullah from Center of Excellence Geopolymer and Green Technology (CEGeoGTech), UniMAP, for his continuous assistance, uncountable help and guidance, throughout the whole process to complete my research. I am very grateful to him for keep having faith and confidence to entrust me with many important projects. The knowledge and experience I've gained throughout the various projects were remarkable.

My gratitude is also extended to lecturers and technicians of School of Materials Engineering, UniMAP, for assisting in putting my research work into action and for their help and guidance during laboratory works. Many thanks also to my friends and fellow course mates, especially for their friendship and advice.

A warm thank you to my beloved special friend Benjamin Daniel for his enormous job reviewing and helping me to correct the English grammar in this dissertation. Also, to those who have helped directly or indirectly, I wish I could have put their names here, thanks for being helpful, cooperative and supportive.

Finally, I give my deepest love to my supportive and loving family members for their continuous support, encouragement, and understanding through these years. Their endless and unconditional love has encouraged and supported me ever since I was born.

## TABLE OF CONTENTS

	<b>PAGE</b>
<b>THESIS DECLARATION</b>	i
<b>ACKNOWLEDGEMENT</b>	iii
<b>TABLE OF CONTENTS</b>	iv
<b>LIST OF TABLES</b>	vii
<b>LIST OF FIGURES</b>	viii
<b>LIST OF ABBREVIATIONS</b>	xii
<b>LIST OF SYMBOLS</b>	xiv
<b>ABSTRAK</b>	xv
<b>ABSTRACT</b>	xvi
<b>CHAPTER 1 INTRODUCTION</b>	
1.1 Background	1
1.2 Problem Statements	4
1.3 Aim and Objectives	6
1.4 Work Scopes	7
1.5 Thesis Outline	9
<b>CHAPTER 2 LITERATURE REVIEW</b>	
2.1 Introduction to Solder Interconnects in Electronic Packaging Assemblies	11
2.2 Soldering Technologies	12
2.2.1 Reflow Soldering	13
2.3 Sn-Pb Solders	16
2.3.1 Effects of Pb Exposure on Human Health	17
2.3.2 Forces and Legislations against Pb-based Solders Utilization	18
2.4 Development of Pb-free Solders	20
2.4.1 List of Pb-free Solders Alternatives	21
2.4.2 Sn-0.7Cu Solder Alloy	23
2.5 Reliability of Pb-free Solder Joints in Electronic Assemblies	27

2.6	Introduction to Pb-free Composite Solders	28
2.6.1	Ceramic-reinforced Composite Solder	30
2.6.2	Sn-0.7Cu + 1.0wt.% Si <sub>3</sub> N <sub>4</sub> Composite Solder	31
2.7	Composite Solder Fabrication via Powder Metallurgy (PM) Routes	33
2.7.1	Mixing/Blending and Forming	34
2.7.2	Sintering	35
2.8	Theoretical Aspects of Microwave Sintering	38
2.9	Summary of Literature Review Findings	42

### **CHAPTER 3 MATERIALS AND EXPERIMENTAL PROCEDURES**

3.1	Experimental Work Overview	44
3.2	Raw Materials	45
3.3	Phase 1: Design, Assembly and Calibration of an Experimental Hybrid Microwave Assisted Sintering Setup	46
3.3.1	Design	46
3.3.2	Temperature Measurements	48
3.4	Phase 2: Synthesis of Monolithic and Composite Bulk Solders	50
3.4.1	Dry Blending	51
3.4.2	Cold Compaction	52
3.4.3	Conventional Sintering	52
3.4.4	Microwave Sintering	53
3.5	Phase 3: Characterization Studies	54
3.5.1	Density and Porosity Measurements	55
3.5.2	Microhardness Testing	56
3.5.3	X-Ray Diffraction (XRD) Analysis	57
3.5.4	Microstructure Characterization of Bulk Solders	57
3.5.5	Solderability Test Preparation	58
3.5.6	Wettability Measurements	59
3.5.7	Intermetallic Compound (IMC) Layer Thickness Measurements	60

### **CHAPTER 4 RESULTS AND DISCUSSION**

4.1	Introduction	61
4.2	Development of Sn-0.7Cu + 1.0wt.% Si <sub>3</sub> N <sub>4</sub> Composite Solder Green Compact	62

4.3	Evaluation of Experimental Hybrid Microwave Assisted Sintering Setup	65
4.3.1	Influence of Microwave Power Output and Microwave Suscepting SiC Crucible on Heating Rate of Setup	65
4.3.2	Hybrid Microwave Heating Behavior of Composite Bulk Solder	67
4.3.3	Influence of Microwave Exposure Time on Microhardness of Bulk Solder	71
4.3.4	Processing Time and Energy Efficiency of Setup	74
4.4	Effects of Different Sintering Methodologies on Properties of Monolithic and Composite Solder	76
4.4.1	Observation of Sintered Bulk Samples	76
4.4.2	Density and Porosity Measurements	77
4.4.3	Microhardness Measurements	81
4.4.4	X-Ray Diffraction (XRD) Analyses	84
4.4.5	Microstructural Characterization	86
4.4.6	Wettability Test on Cu-substrate	96
4.4.7	IMC Thickness of the as-reflowed Solder on Cu-substrate	99
4.5	Overall Results and Summary of Findings	101
<b>CHAPTER 5 CONCLUSIONS AND RECOMMENDATIONS</b>		
5.1	Conclusions	103
5.2	Recommendations	105
<b>REFERENCES</b>		
<b>APPENDIX A</b>		
<b>APPENDIX B</b>		
<b>APPENDIX C</b>		
<b>APPENDIX D</b>		
<b>LIST OF PUBLICATIONS</b>		

## LIST OF TABLES

NO.		PAGE
1.1	Sintering control factor allocation in this research.	8
2.1	Pb-poisoning effects in human (EPA, 2012).	17
2.2	List of various categories of typical Pb-free solder alloys (AIM Solder, 2006).	22
2.3	Characteristic of the Sn-0.7Cu + Xwt.% Si <sub>3</sub> N <sub>4</sub> composite solder fabricated via PM methods (Mohd Salleh et al., 2011, 2012).	32
3.1	Description of materials used in the research.	45
3.2	Function description of the design features for hybrid microwave assisted sintering setup.	47
3.3	Power setting of microwave SANYO oven.	48
3.4	Description of synthesized solders systems.	50
4.1	Energy consumption analysis of conventional and hybrid microwave assisted sintering process.	75
4.2	Density and porosity of SC and SC1SN.	78
4.3	Results of Vickers microhardness across the diameter of sintered SC and SC1SN bulk solders.	81
4.4	Morphological characteristic of grains.	93
4.5	Overall results in this research work.	102

## LIST OF FIGURES

NO.		PAGE
1.1	Number of publications retrieved from Scopus website database by year when using the search term “lead-free composite solder” and “lead-free composite solder AND powder metallurgy” in the Article Title, Abstract, and Keywords fields for all document types.	2
2.1	The typical hierarchy of electronic packaging technologies in electronic products (Illyefalvi-Vitéz et al., 1999).	12
2.2	The general stages and features in reflow soldering profile (Viyari, 2007).	14
2.3	The Sn-0.7Cu composition in Cu-Sn binary phase diagram (ASM International, 1992).	24
2.4	The optical micrograph of as-solidified Sn-0.7Cu showing the large $\beta$ -Sn grains or dendrites (grey area) surrounded by a network of the lamellar eutectic (dark area) structure containing $\beta$ -Sn and fine intermetallic Cu <sub>6</sub> Sn <sub>5</sub> structures (Wu & Huang, 2002).	24
2.5	Interfacial IMC layer of Sn-0.7Cu solder-Cu joint (a) as-soldered at 260 °C and thermally aged at 150 °C for (b) 10 days and (c) 20 days (Wang et al., 2005).	26
2.6	Schematic illustration showing the damage (D) resulting from multiple fields and their complex interactions that affects the reliability of electronic solder joints (Subramanian, 2012).	27
2.7	Diagram of typical powder metallurgy (PM) process routes used in composite manufacturing industry (MPIF, n.d.).	34
2.8	Schematic diagram of two-directional microwave assisted rapid sintering setup inside normal household microwave oven (Gupta & Wong, 2005).	37
2.9	Schematic of two-directional heating during hybrid microwave assisted sintering (Gupta & Leong, 2007).	37
2.10	Schematic diagram showing materials interaction with microwaves: (a) transparent, (b) opaque, and (c) absorber (Oghbaei & Mirzaee, 2010).	39
3.1	Flow chart of the research work.	44
3.2	Schematic diagram of the experimental hybrid microwave assisted sintering setup.	46
3.3	Photograph showing the actual plan view of the hybrid microwave assisted sintering setup cavity.	47

3.4	Schematic illustration showing the temperature measurements in three different arrangement conditions inside the setup cavity; (A) without SiC crucible and without sample, (B) with SiC crucible and without sample, (C) with SiC crucible and with sample.	49
3.5	Flow chart of synthesis of monolithic and composite bulk solder samples.	51
3.6	Conventional sintering profile for SC and SC1SN green compact samples.	53
3.7	Flow chart of characterization studies.	54
3.8	Electronic Density Hydrometer HZ-2712 for bulk density measurement.	56
3.9	Reflow profile used for the F4N reflow oven.	58
3.10	Schematic illustration of sample preparation for solderability test.	59
3.11	Illustration of the area of IMC layer and length of the measured area.	60
4.1	SEM secondary electron images of as-received raw powder particles: (a) Sn-0.7Cu powder and (b) Si <sub>3</sub> N <sub>4</sub> powder.	62
4.2	SEM secondary electron images of mechanical mixture of SC1SN composite prepared by dry blending.	63
4.3	SEM backscattered electron shadow (BES) image of SC green compact sample at 500X magnification. Insert is the OM micrograph showing clear image of pores and grain structure of the deformed Sn-0.7Cu particles.	63
4.4	SEM backscattered electron shadow (BES) images at 100X magnification showing the distribution of Si <sub>3</sub> N <sub>4</sub> particles (dark inclusions). Insert shows the 500X magnification of the SEM image.	64
4.5	Effect of microwave power output with and without SiC crucible on the heating rate of setup. Measured without the presence of green compact sample.	66
4.6	Heating behavior of SC1SN compact when sintered using the experimental hybrid microwave assisted sintering setup at 800 W.	68
4.7	Schematic diagram illustrating the (a) microwave energy directions into the setup cavity and the (b) hybrid heating mechanisms inside the setup cavity resulted from the microwave energy. Notes that the sample experienced hybrid heating both from its interaction between microwave energy (green arrows) and radiant heat (red arrows) from susceptors.	70
4.8	Influence of microwave exposure time on average microhardness of SC and SC1SN samples. The indicated temperatures were obtained from the heating behavior of SC1SN compact.	71

4.9	Representative SC (a, b, c) and SC1SN (d, e, f) compacts surfaces before (Usint) and after sintering (Csint, Msint) taken using stereo microscope.	76
4.10	Photographs showing the representative SC and SC1SN bulk solder compacts after conventionally and microwave sintered. Swelling can be seen in SC/Csint sample.	77
4.11	(a) Density and (b) porosity against methods of sintering for SC and SC1SN samples.	78
4.12	Schematic illustration showing the microhardness indentations at selected points across the diameter of the bulk solder sample.	81
4.13	Microhardness measurements against methods of sintering for SC and SC1SN samples before (bulk only) and after reflowed on Cu-substrate.	83
4.14	Schematic illustration showing microhardness indentation points of bulk solder samples reflowed on Cu-substrate.	84
4.15	X-ray diffractograms of the unsintered, conventionally sintered and microwave sintered of (a) SC and (b) SC1SN samples.	85
4.16	EDS analysis results as indicated in SEM micrograph of (a) SC1SN/Msint sample at point (b) 001, (c) 002 and (d) 003.	87
4.17	OM micrograph showing the monolithic SC grains structure at 50X magnification in (a) SC/Usint, (b) SC/Csint and (c) SC/Msint solder samples.	88
4.18	OM micrograph showing the base matrix particles grains and Si <sub>3</sub> N <sub>4</sub> distribution in (a) SC1SN/Usint, (b) SC1SN/Csint and (c) SC1SN/Msint at 50X magnification.	89
4.19	OM micrographs of SC samples (left side) at 20X magnification showing clear morphological features of the Sn-0.7Cu grains particles. The binary images (right side) of the grain structures edited in ImageJ processing software shows the complete grain (highlighted in grey) within the micrographs perimeter.	91
4.20	The original OM micrographs (a, b, c) of SC1SN microstructure at 20X magnification. The reinforcement particle distribution in the micrographs (b, d, f) dispersed at the grain boundaries are highlighted as red using threshold process in ImageJ software.	92
4.21	Frequency distributions of grains size (area) in SC bulk solders with different sintering approach.	94
4.22	OM micrographs (left side) of SC microstructures at 10X magnification in: (a) unsintered, (b) conventionally sintered, and (c) microwave sintered samples. The post-processing binary images (right side) show the full grains within the respective micrographs.	95
4.23	A representative OM micrograph showing the contact angle ( $\theta$ ) measurement.	97

4.24	Contact angle measurements on Cu-substrate against method of sintering for SC and SC1SN solder samples.	97
4.25	OM micrographs in the cross-sectional view of the as-reflowed solder-substrate interface.	99
4.26	IMC thickness measurements of SC and SC1SN on Cu-substrate for conventional and microwave sintering.	100

© This item is protected by original copyright

## LIST OF ABBREVIATIONS

Ag	Silver
Al <sub>2</sub> O <sub>3</sub>	Alumina
Au	Gold
Bi	Bismuth
Cd	Cadmium
Cr <sup>6+</sup>	Hexavalent Chromium
CTE	Coefficient of Thermal Expansion
Cu	Copper
EDX	Energy Dispersive X-ray
EEE	Electrical and Electronic Equipment
EPA	Environmental Protection Agency
EU	European Union
HCl	Hydrochloric acid
Hg	Mercury
HNO <sub>3</sub>	Nitric acid
IC	Integrated Circuit
IMC	Intermetallic Compound
In	Indium
ISM	Industrial, Scientific and Medical
ISO	International Standard Organization
MCV	Maximum Concentration Value
MMC	Metal-matrix Composite
NC	No-Clean
NEMI	National Electronics Manufacturing Initiative
Ni	Nickel
N	Nitrogen
OM	Optical Microscope
Pb	Lead
PBB	Polybrominated Biphenyls
PBDE	Polybrominated Diphenyl Ethers
PCB	Printed Circuit Board

PD	Penetration Depth
PM	Powder Metallurgy
PWA	Printed Wiring Assembly
RoHS	Restriction of the Use of certain Hazardous Substances in Electrical and Electronic Equipment
SAC	Sn-Ag-Cu
SEM	Scanning Electron Microscope
Si	Silicon
Si <sub>3</sub> N <sub>4</sub>	Silicon Nitride
SiC	Silicon Carbide
SMT	Surface Mount Technology
Sn	Tin
SnO <sub>2</sub>	Tin Oxide
TiB <sub>2</sub>	Titanium Diboride
VPS	Vapour Phase Soldering
WEEE	Waste Electrical and Electronic Equipment
XRD	X-ray Diffraction
ZrO <sub>2</sub>	Zirconia

© This item is protected by original copyright

## LIST OF SYMBOLS

$T_m$	Melting temperature
$\lambda$	Wavelength
$\rho$	Density
$v$	Volume

© This item is protected by original copyright

## **Fabrikasi dan Pencirian Pateri Komposit Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> Disinter Secara Hibrid Melalui Bantuan Gelombang Mikro**

### **ABSTRAK**

Salah satu kaedah untuk meningkatkan ciri-ciri aloi pateri bebas plumbum yang sedia ada adalah melalui pendekatan teknologi komposit, di mana partikel-partikel seramik berteknikal tinggi boleh ditambah masuk ke dalam matriks aloi pateri. Oleh yang demikian, pateri komposit Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> telah disintesis menggunakan kaedah-kaedah metalurgi serbuk yang terdiri daripada proses pengadunan, pepadatan dan pensinteran di dalam kajian ini. Kajian ini juga telah memperkenalkan proses pensinteran secara hibrid melalui bantuan gelombang mikro yang berkebolehan untuk mensinter pateri komposit bertetulang seramik pada suhu 185 °C dalam masa 2 minit tanpa masa pemanasan dan perlindungan gas lengai. Dalam usaha untuk menilai keserasian pendekatan pensinteran secara hibrid melalui bantuan gelombang mikro terhadap pembangunan pateri komposit bertetulang seramik, perbandingan pemprosesan dan sifat-sifat pateri komposit Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> melalui kaedah pensinteran konvensional dan pensinteran gelombang mikro telah dijalankan dengan lebih terperinci. Suhu pensinteran yang sama iaitu 185 °C telah digunakan untuk kedua-dua jenis pensinteran, di mana pensinteran konvensional dilakukan di dalam tiub relau dengan kehadiran gas argon selama 2 jam. Sampel pateri monolitik Sn-0.7Cu juga telah disintesis sebagai sampel kawalan dengan cara yang sama. Pensinteran secara hibrid melalui bantuan gelombang mikro menunjukkan kelebihan dalam pemprosesan berbanding kaedah pensinteran konvensional, seperti kadar pemanasan yang tinggi, masa pensinteran yang singkat, kadar penggunaan tenaga yang kurang dan peralatan yang jauh lebih murah. Pengaruh perbezaan metodologi pensinteran pada sampel pateri komposit Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> telah dikaji berdasarkan ketumpatan, keliangan, kekerasan, mikrostruktur, kebolehasahan dan ketebalan sebatian antara logam ke atas Cu-substrat. Didapati bahawa kaedah pensinteran secara hibrid melalui bantuan gelombang mikro mampu memadatkan kompakan pateri komposit Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> dalam masa yang lebih singkat, bagaimanapun, kaedah pensinteran konvensional di dalam kajian ini menunjukkan kepadatan dan keliangan sampel yang lebih baik. Menariknya, mendakan yang lebih halus dan agihan mendakan yang lebih menyeluruh telah diperhatikan dalam sampel gelombang mikro tersinter. Hal ini juga telah membawa kepada peningkatan prestasi kekerasan pada sampel gelombang mikro tersinter (12.0 ± 0.2 HV) berbanding dengan sampel konvensional tersinter (11.2 ± 0.1 HV). Prestasi kebolehasahan Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> pada Cu-substrat telah dikurangkan sedikit dengan pendekatan pensinteran gelombang mikro, walaubagaimanapun, perbezaan ketebalan sebatian inter metalik yang tidak ketara telah diperhatikan bagi kedua-dua sampel gelombang mikro tersinter dan sampel konvensional tersinter. Secara keseluruhannya, kaedah pensinteran hibrid melalui bantuan gelombang mikro telah menunjukkan pemprosesan yang lebih baik dengan ciri-ciri yang menjanjikan pada seramik bertetulang pateri komposit Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub>.

## **Fabrication and Characterization of Hybrid Microwave Assisted Sintering Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> Composite Solder**

### **ABSTRACT**

One of the leading choices in upgrading the properties of existing lead-free solder alloys is by composite technology approach, whereby high technical ceramic particles can be added into the solder alloy matrix. Accordingly, Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite solder was synthesized using powder metallurgy routes which consist of blending, compaction and sintering. This research introduced a hybrid microwave assisted sintering process which can sinter ceramic-reinforced composite solder at approximately 185 °C within 2 minutes without holding time and protective inert gas. In order to evaluate the compatibility of hybrid microwave assisted sintering approach in ceramic-reinforced composite solder development, a detailed comparison of the process and properties of conventionally sintered and microwave sintered samples of Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite solder was performed. Identical sintering temperature at 185 °C was used for both types of sintering, in which conventional sintering was performed using a tube furnace in an argon atmosphere for 2 hours. The monolithic Sn-0.7Cu solder sample was also synthesized as control sample in a similar way. Hybrid microwave assisted sintering method showed significant advantages in processing compared to conventional sintering method, such as rapid heating rate, shortened sintering time, less energy consumption and much less expensive equipment. The influence of different sintering methodologies on Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> bulk solder sample were investigated based on the density, porosity, microhardness, microstructures, wettability and intermetallic compound thickness on Cu-substrate. It was noted that microwave sintering method can densify the Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite bulk solder green compact in a short time, however, conventional sintered sample showed better density and porosity. Interestingly, finer and well-distributed precipitates were observed in microwave sintered samples. This has led to higher microhardness performance observed in microwave sintered sample ( $12.0 \pm 0.2$  HV) compared to the conventionally sintered sample ( $11.2 \pm 0.1$  HV). The wettability performance of Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite solder on Cu-substrate was slightly reduced with microwave sintering approach, however, insignificant difference of intermetallic compound thickness was observed in both microwave sintered and conventionally sintered samples. Overall, hybrid microwave assisted sintering showed better processing with promising properties on ceramic-reinforced Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite solder.

# CHAPTER 1

## INTRODUCTION

### 1.1 Background

Over the past few years, the electronic packaging industry is constantly adapting to consumer demands for more advanced electronic devices. According to Accenture (2013) annual report, the current trend of electronics products shows the consumers' purchase intentions are focused on multi-function devices that can offer convenient handling, such as smartphones, tablets, personal computers and high-definition televisions. As a consequence, there are increasing demands for higher interconnections count to be expected in a smaller electronic package. This has led to an urgent need for development of new solder interconnects that can provide high dimensional stability and reliability of joints during processing and usage. Lead-free solders and its soldering processing have been well established in the electronic packaging industry. Interconnect technology is, in fact, presently restructuring towards the second generation of lead-free solder materials (Schueller et al., 2010).

One of the possible choices in upgrading the existing lead-free solder alloys is by introducing secondary particles in the alloy matrix so as to form lead-free composite solder (Guo, 2007). Previous studies on composite solder as summarized by Liu et al. (2012) have shown some valuable results that proved composite solder can effectively enhance solder joint performance. Besides, the number of publications per year retrieved from the Scopus database also shows a clear rising interest within the research community

in studying lead-free composite solder (see Figure 1.1). Whilst there has been a recent interest detected within the publications to combine lead-free composite solder and powder metallurgy (PM) method.

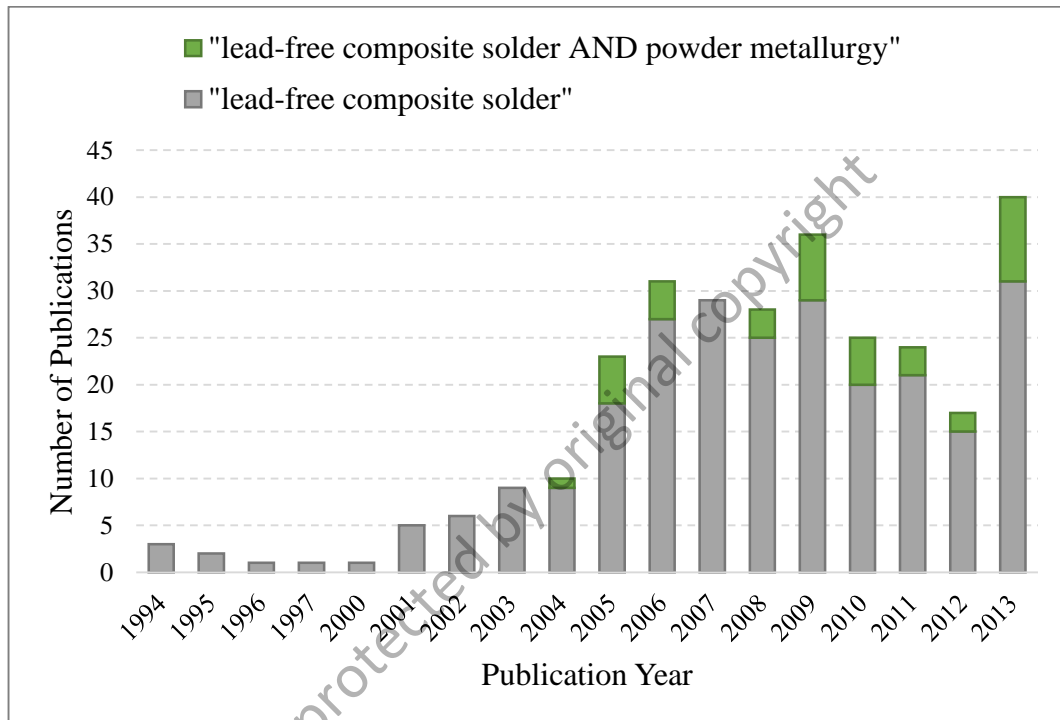


Figure 1.1: Number of publications retrieved from Scopus website database by year when using the search term “lead-free composite solder” and “lead-free composite solder AND powder metallurgy” in the Article Title, Abstract, and Keywords fields for all document types.

Accordingly, this study is carried out to explore the increasing research interest in composite solder using ceramic reinforcement materials through PM routes. Although the PM method was regularly utilized among the researchers to synthesis ceramic-reinforced composite solder (Mohd Salleh et al., 2013), the sintering step is still quite a challenge as it consumes significant amount of energy, time, and cost. Thus, there exists a great need for exploring advance heating method capable of providing a rapid heating rate for the sintering of ceramic-reinforced composite solder compacts.

Literature studies show microwaves can be utilized to sinter composite solder when in compacted powder form (Rybakov et al., 2013). Gupta and Wong (2005) have successfully produced an experimental setup that utilizes energy efficient two-directional microwave heating mechanism that is capable of sintering metal-based materials rapidly. The two-directional microwave assisted heating mechanism may also be called hybrid sintering. This is because the heating of the compacted powder come from two directions, i.e., direct heating within the compact materials and radiant heating from the microwave susceptor material arranged around the compact.

Further investigation has been carried out by Babaghorbani and Gupta (2008) to compare the effects of different sintering methodologies, i.e., conventional radiant sintering and the prior hybrid microwave assisted sintering setup initially developed by Gupta and Wong (2005) on the commercial lead-free Sn-3.5Ag solder alloy compacts. It was revealed that the tensile properties of Sn-3.5Ag samples were enhanced when using microwave assisted sintering method approach. The microwave sintered Sn-3.5Ag samples showed 21%, 17%, and 19% higher in 0.2% yield strength, ultimate tensile strength, and work of fracture, respectively, when compared to conventionally sintered samples.

In fact, ceramic-reinforced Sn-0.7Cu/Al<sub>2</sub>O<sub>3</sub> and Sn-3.5Ag/SnO<sub>2</sub> composite solders have been successfully synthesized by Nai et al. (2010) using the same experimental hybrid microwave assisted sintering setup. It was found that the microwave technology can be a great assistant in a sintering process since it consumes much lower energy than conventional sintering with lesser heating time.

## 1.2 Problem Statements

Among the developed lead-free solders available in the market nowadays, eutectic Sn-0.7Cu solder alloy was widely used as the alternative standard for both lead- and silver-free solder alloys. However, eutectic Sn-0.7Cu solder alloy has a high tin (Sn) composition which can induce coarsening of phases within the solder matrix and the solder/substrate interfaces when imposed by thermal stress for a period of time. Moreover, eutectic Sn-0.7Cu solder alloy has low mechanical properties credibility since this alloy composition prone to brittle whisker intermetallic compound growth that can leads to serious reliability issues (Delserro, 2006). Recent studies attempted by various researchers to reincorporate small addition of non-reactive secondary particle such as  $\text{Al}_2\text{O}_3$ ,  $\text{ZrO}_2$ , and  $\text{Si}_3\text{N}_4$  (Zhong & Gupta, 2008a, 2008b; Mohd Salleh et al., 2012) to form composite solders have shown great enhancement in mechanical properties of the monolithic Sn-0.7Cu solder matrix. Hence, more efforts should be done on upgrading the promising lead-free Sn-0.7Cu alloy solder through composite technology.

In electronic packaging, lead-free solders are used to join a ceramic cap and a multilayer ceramic substrate in a multichip module. However, the solder joint suffers from a poor resistance to thermal fatigue since the monolithic solder alloy generally has much higher thermal expansion coefficient (CTE) than that of a ceramic (Tong, 2011). Since there is a need for a solder with a low CTE, the composite solder can be modified using specific ceramic reinforcement that possess low CTE properties. Among the various ceramic reinforcement materials that have been introduced in the lead-free composite solder development nowadays, the high technical ceramic materials such as  $\text{Si}_3\text{N}_4$  can be a great candidate as a reinforcement material to enhance the monolithic Sn-0.7Cu solder matrix. Accordingly,  $\text{Si}_3\text{N}_4$  is a light ceramic material with a low CTE and has been

widely used for extreme engineering applications because of its excellent mechanical performance at both ambient and elevated temperatures (Trice & Halloran, 2000). Prior studies have simultaneously shown improvement in both solderability and mechanical performance in Sn-0.7Cu solder matrix by adding 1.0 weight percentage (wt.%) of micron-sized Si<sub>3</sub>N<sub>4</sub> particles (Mohd Salleh et al., 2011, 2012). Realizing the capability of the Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite solder, more testing should be done on such composition to fully explore the composite solder potential.

The ideal way to reincorporate ceramic powder particulates into the monolithic solder matrix is by utilizing PM routes under solid state processing consist of mixing, compaction, and sintering. However, the sintering step consumes significant amount of energy, time, and cost. Regarding the sintering step, literature studies showed microwave technology can be utilized to sinter composite solder in compacted powder form. Among the primary advantages given by this method are microwave assisted sintering consumes much lower energy with lesser heating time compared with conventional sintering method. Usually, enhanced mechanical properties of ceramic-reinforced composite material can be obtained with finer microstructures distribution. While, fine microstructures distribution can be obtained through the manipulation of sintering temperature and time. Microwave technology can be a great assistant in a sintering process since the heat produced by this method is self-generated by the sintered material. Hence, its utilization in ceramic-reinforced lead-free composite solder is highly recommended.

The result of the literature search at the start of this present research revealed that no hybrid microwave assisted sintering work has been made to synthesize ceramic-reinforced Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite solder. Accordingly, the purpose of this research is to evaluate the possibilities of implementing hybrid microwave assisted

sintering technique through powder metallurgy routes, particularly for ceramic-reinforced Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite solder production. The nature of the topic focuses on the impact of different sintering methodologies related to processing and properties of Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite solder, since comparisons of the sintering adaptation of powder metallurgy made with different sintering techniques are still lacking.

### 1.3 Aim and Objectives

The main aim of this research is to clarify any properties enhancement or advantages that hybrid microwave heating process can possibly offer if such attempt is preferred rather than conventional radiant heating on Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite solder. The research intends to achieve this aim through the following objectives:

- i) To assemble and calibrate an experimental set-up capable of sintering solder compacts using both microwave heating and radiant heating simultaneously.
- ii) To synthesize Sn-0.7Cu monolithic solder and Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite solder via powder metallurgy routes using different sintering methodologies, i.e., without sintering, with conventional sintering, and with hybrid microwave assisted sintering.
- iii) To investigate the influence of different sintering methodologies on the density, porosity, microhardness, microstructure, and solderability performance of Sn-0.7Cu monolithic solder and Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite solder.

## 1.4 Work Scopes

In order to strategically reach these objectives, the work scope of this study is divided into three phases as described in the following:

- A. Phase 1 – Design, assembly and calibration of an experimental hybrid microwave assisted sintering setup.

The initial phase of this study is the assembly of an experimental hybrid microwave assisted sintering setup that will be used for the sintering of Sn-0.7Cu + 1.0wt.% Si<sub>3</sub>N<sub>4</sub> composite solder compacts in Phase 2. The hybrid term in the design of microwave assisted sintering was intended since the heating element is comprised both from microwave energy source and radiant heating from microwave susceptor material. In this present study, a domestic household microwave oven was used to generate microwave energy and SiC (silicon carbide) crucible was chosen as the microwave susceptor material to be placed inside the setup cavity. The design, however, does have some limitations and constraints. The size of the normal household microwave oven and the SiC crucible gained through this study itself is designed for small sample. Thus, very large sample could not be used. Table 1.1 shows the sintering control factor allocation in this research. The setup was calibrated to determine the appropriate microwave exposure time for the setup to reach the sintering temperature. Microwave sintering of sample in an inert gas was not possible due to the inability of the setup to purge gas in and out from the heating cavity. Hence, hybrid microwave assisted sintering was performed under ambient atmospheric condition without the presence of inert protective gas.